

# Influence of the Curing Mode on Fluoride Ion Release of Self-adhesive Resin Luting Cements in Water or During pH-Cycling Regimen

TR Aguiar • CF Pinto • V Cavalli  
M Nobre-dos-Santos • GMB Ambrosano • P Mathias  
M Giannini

## Clinical Relevance

Within the limited experimental conditions, the self-adhesive cements provided fluoride ion release capacity. The fluoride release for all resin cements was not uniform during pH cycling, decreasing throughout the duration of the study.

---

\*Thaiane Rodrigues Aguiar, DDS, MS, PhD student, Department of Restorative Dentistry, Piracicaba School of Dentistry, University of Campinas, Piracicaba, Brazil

Cristiane Franco Pinto, DDS, MS, PhD, Department of Restorative Dentistry, São Francisco School of Dentistry, São Francisco University, Bragança Paulista, Brazil

Vanessa Cavalli, DDS, MS, PhD, Division of Operative Dentistry, Department of Dentistry, University of Taubaté, Taubaté, São Paulo, Brazil

Marinês Nobre-dos-Santos, DDS, MS, PhD, Department of Pediatric Dentistry, Piracicaba School of Dentistry, State University of Campinas, Piracicaba, São Paulo, Brazil

Glaucia Maria Bovi Ambrosano, DDS, MS, PhD, Community Dentistry Department, Piracicaba School of Dentistry, State University of Campinas, Piracicaba, SP, Brazil

Paula Mathias, DDS, MS, PhD, Department of Restorative Dentistry, Federal University of Bahia, Salvador, Bahia, Brazil

## SUMMARY

**This study evaluated the effects of curing modes and storage conditions on fluoride release of resin cements. In phase 1, the cumulative fluoride release rate from samples of the resin cements (Panavia F 2.0, RelyX Unicem, MaxCem, and BisCem) was quantified after 15 days storage in water (n=4). In phase 2,**

---

Marcelo Giannini, DDS, MS, PhD, Department of Restorative Dentistry, Piracicaba School of Dentistry, University of Campinas, Piracicaba, Brazil

\*Corresponding author: Department of Restorative Dentistry, Piracicaba School of Dentistry, State University of Campinas, Av Limeira, 901, Piracicaba, SP, Brazil 13414-900; e-mail: giannini@fop.unicamp.br

DOI: 10.2341/10-328-L

---

the fluoride release profiles from the same materials were analyzed during pH cycling ( $n=4$ ). In this second phase, fluoride was measured at specific times (one, two, three, five, eight, and 15 days). Disk-shaped specimens were prepared ( $10\text{ mm} \times 0.5\text{ mm}$ ), and the materials were either light activated or allowed to autopolymerize. For both phases, the fluoride release was measured using a fluoride ion-specific electrode. The fluoride release in water was not affected by the curing mode of RelyX Unicem and Maxcem resin cements. Panavia F. 2.0 and BisCem resin cements, either light cured or autopolymerized modes, released higher amounts of fluoride in water than the other self-adhesive cements. In phase 2, the concentration of fluoride released decreased from the first day of pH cycling until the 15th day for all resin cements, for both curing modes, regardless of the storage solution used (demineralizing/remineralizing). The fluoride release rate during pH cycling by Panavia F 2.0 and MaxCem was not affected by the curing mode. The effect of the curing mode on fluoride ion release in water or during pH cycling was product dependent.

## INTRODUCTION

Fluoride application to tooth structures has influenced the decline in the prevalence and severity of dental caries.<sup>1,2</sup> Many studies have shown that the ion is safe and effective in preventing and controlling caries development under specific dosages. Such benefits are due to its ability to inhibit the demineralization and enhance remineralization.<sup>3-5</sup>

A number of studies have suggested that the fluoride released from glass ionomer cements can reduce the demineralization of the surrounding dentin or enamel and favor the remineralization of lesions close to the restoration wall.<sup>6-9</sup> Glass ionomer cements contain calcium fluoroaluminosilicate glass, which is attacked by polyacids to release cations and fluoride ions. These ions react with polyanions to form a salt gel matrix that presents small particles of silica gel containing fluoride crystallites. The preventive and therapeutic effects of glass ionomer cements are attributed to the discharge of fluoride ions, and this releasing does not affect the physical properties of the cement.<sup>10</sup>

Other fluoride-containing restorative materials, such as restorative composites, resin cements, and adhesive systems, have been developed to prevent recurrent caries; however, glass ionomer cements

show a fluoride-recharging ability and have demonstrated more prolonged fluoride release than these materials. Most of these resin-based materials contain different fluoride sources, and the amount of fluoride released seems to depend on the brand and other characteristics of each material.<sup>9,11-15</sup>

The self-adhesive resin cements were recently developed, and the main advantages of using these materials include a shorter clinical application time and technique sensitivity reduction.<sup>16-19</sup> In addition, self-adhesive resin cements contain different fluoride sources, and limited information is available regarding their ability to release sufficient fluoride concentrations in water or during a cariogenic challenge. Thus, the purpose of this study was to evaluate the effects of curing modes and storage conditions on fluoride release from dual-polymerizing resin cements. The research hypotheses tested were that 1) curing mode affects the amount of fluoride release in water, regardless of type of resin cement used, and 2) the fluoride release profile of resin cements is uniform during pH cycling, regardless of the resin cement and the curing mode.

## METHODS AND MATERIALS

### Sample Preparation

Three self-adhesive dual-polymerizing resin cements, RelyX Unicem (3M ESPE, Seefeld, Germany), MaxCem (Kerr Corp, Orange, CA, USA), and BisCem (Bisco Inc, Schuamburg, IL, USA), and one conventional dual-polymerizing cement (Panavia F 2.0, Kuraray Med, Kurashiki, Japan) were used according to the manufacturers' instructions (Table 1).

Sixteen disks of each resin cement were prepared (total = 64 samples). The mixed base and catalyst pastes were dropped into individual cylindrical silicon molds ( $10.0\text{ mm}$  diameter  $\times$   $0.5\text{ mm}$  depth, Aquasil Ultra LV, Dentsply Caulk, Milford, DE, USA), covered with a polyester strip and pressed with one microscope glass slide. Half of the total samples (32 discs) were light cured for 40 seconds (XL 3000, 3M ESPE, St Paul, MN, USA), and the other half were allowed to autopolymerize only. Thirty-two resin cement discs were evaluated according to the cumulative fluoride release rate in water, and thirty-two samples were prepared for fluoride release profiles during the pH-cycling regimen. All resin cement samples were stored at  $37^\circ\text{C}$  for 48 hours ( $n=4$ ). A schematic diagram of the study design is shown in Figure 1. After curing, the disk-shaped samples were removed from the silicon molds, and the excess material was removed using

Table 1: Compositions of the Resin Cements Used in This Study

Resin Cement	Composition
Panavia F 2.0	<p>Paste A: 10-MDP, silanated colloidal silica, bisphenol A polyethoxy dimethacrylate, hydrophobic and hydrophilic DMA, silanized silica filler, benzoyl peroxide, dl-camphorquinone</p> <p>Paste B: hydrophobic and hydrophilic DMA, sodium 2,4,6-triisopropyl benzene sulphonate, N,N-diethanol-p-toluidine, bisphenol A polyethoxy dimethacrylate, colloidal silica, sodium fluoride, silanized barium glass filler, silanized titanium oxide</p>
RelyX Unicem (capsules)	<p>Power: glass powder, silica, calcium hydroxide, self-curing initiators, pigments, light-curing initiators, substituted pyrimidine, peroxy compound</p> <p>Liquid: methacrylated phosphoric esters, dimethacrylates, acetate, stabilizers, self-curing initiators, light-curing initiators</p>
MaxCem	Multifunctional DMAs, GPDM, proprietary Redox initiators and photoinitiators, barium, fluoroaluminosilicate, fumed silica (66 wt.%)
BisCem	Bis-GMA, uncured dimethacrylate monomer, phosphate acid monomer, glass filler
<p>Abbreviations: 10-MDP, 10-methacryloyloxydecyl dihydrogen phosphate; Bis-GMA, bisphenol-A-diglycidylether dimethacrylate; DMA, dimethacrylates; GPDM, glyceroldimethacrylate dihydrogen phosphate; TEGDMA, triethylene glycol dimethacrylate.</p>	

600-grit SiC paper. Samples were individually fixed to orthodontic steel wires, allowing each to be suspended in each storage media.

### Cumulative Fluoride Release Rate in Water

The self-cured and light-activated samples ( $n=4$ ) were placed into polyethylene vials containing 2 mL of deionized water and individually stored for 15 days. The water was not renewed daily, and 1 mL of each vial was collected for the analysis of fluoride release. TISAB III (total ionic strength adjustment buffer, Orion Research Inc, Cambridge, MA, USA) was added to the collected samples at a ratio of 1:10 (buffer:sample), and the quantification of fluoride in water was carried out by an ion-selective electrode (96-06, Orion Research Inc, Cambridge, MA, USA), connected to an ion analyzer (Orion 720 A model potentiometer, Orion Research Inc, Cambridge, MA, USA), which was previously calibrated with a series of standard solutions. The concentration of fluoride released was expressed in  $\mu\text{g}/\text{cm}^2$ , and the data were analyzed by Kruskal-Wallis and Dunn tests ( $p<0.05$ ).

### Fluoride Release Profile During pH-Cycling Regimen

The self-cured and light-activated samples were submitted to 15 days of a pH-cycling regimen, simulating caries development ( $n=4$ ).<sup>9,20</sup> Each day or cycle consisted of the individual immersion of the

disk-shaped specimen in demineralizing solution (1.4 mM Ca, 0.9 mM P, 0.05 M acetate buffer, pH 5.0, 2 mL per specimen) for eight hours and remineralizing solution (1.5 mM Ca, 0.9 mM P, 0.1 M Tris buffer, pH 7.0, 2 mL per specimen) for 16 hours. The solutions (demineralizing and remineralizing) were renewed daily, and 1 mL of each solution was collected at the first, second, third, fifth, eighth, and 15th days for the analysis of fluoride release, which was carried out by the same methodology previously used.

Fluoride release was also recorded in  $\mu\text{g}/\text{cm}^2$ . Mann-Whitney and Wilcoxon tests were used to analyze the influence of curing modes and storage media (demineralizing and remineralizing solutions) on fluoride release, respectively ( $p<0.05$ ). The Friedman Non-Parametric Repeated Measures Comparisons analyzed the fluoride release profile during the pH-cycling regimen ( $p<0.05$ ).

## RESULTS

The results of the experimental groups and the amount of fluoride released after 15 days of storage in deionized water for each resin cement in both curing modes are displayed in Table 2. The fluoride release of RelyX Unicem and MaxCem self-adhesive resin cements was not affected by curing mode, while light activation significantly increased the fluoride releasing of Panavia F 2.0 and decreased the

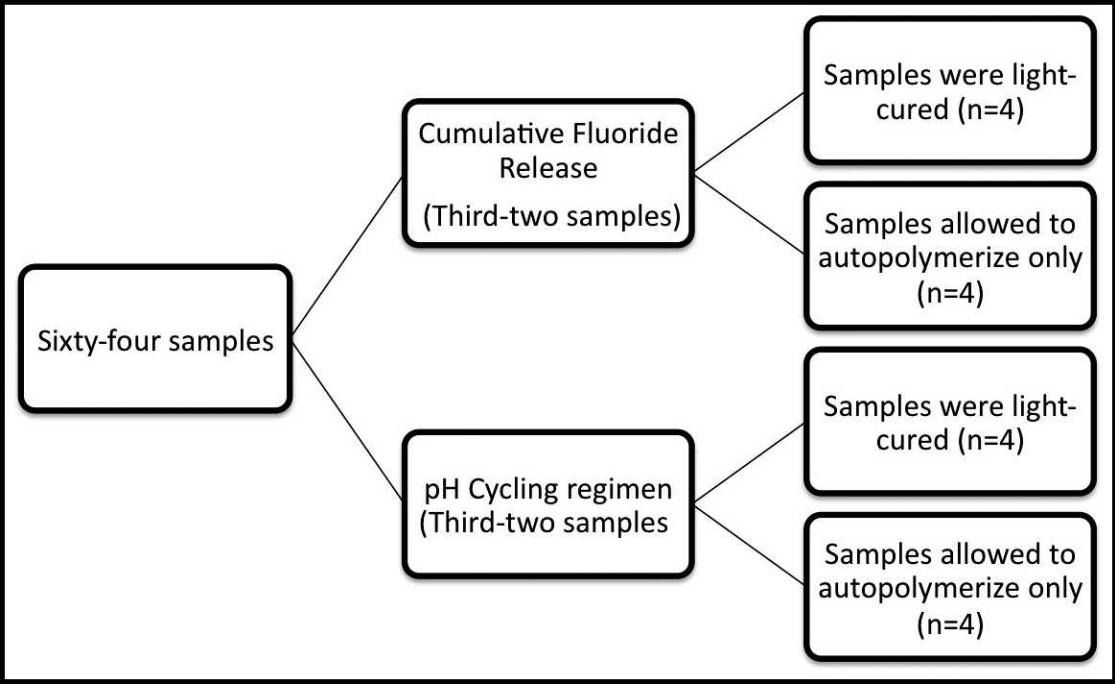


Figure 1. Schematic diagram of study design: Four resin cements were tested in this study (Panavia 2.0, RelyX Unicem, MaxCem, and BisCem).

releasing for BisCem self-adhesive cement. BisCem and Panavia F 2.0 released more fluoride ions in water than RelyX Unicem and MaxCem self-adhesive resin cements in both curing modes.

The fluoride release profiles during the pH-cycling regimen of the resin cements at each period are shown in Figures 2 (Panavia F 2.0, RelyX Unicem), 3 (MaxCem), and 4 (BisCem). In general, the concentration of fluoride released tended to decrease significantly from the first to the 15th day of pH

cycling, regardless of the curing mode and storage solution (demineralizing/remineralizing) used.

For Panavia F 2.0 and MaxCem resin cements (Figures 2 and 4, respectively), the amount of fluoride released in the demineralizing or remineralizing was not affected by the curing mode at any time. Also, the fluoride concentration in the remineralizing solutions of these resin cements was higher than in the demineralizing solutions on the first day. At the second day, the four groups of Panavia F 2.0 resin cement released similar concentrations of fluoride until the 15th day, which tended to reduce the concentration to zero.

Fluoride-releasing behavior for RelyX Unicem during the pH-cycling regimen (Figure 3) showed that the autopolymerized samples released more fluoride ions in both demineralizing and remineralizing solutions than light-activated samples at the first day. RelyX Unicem and MaxCem self-adhesive resin cements continued to release fluoride until the 15th day, and the concentration measured in the solutions varied from 0.015 to 0.005  $\mu\text{g}/\text{cm}^2$  (Figures 3 and 4, respectively). From the second day until the 15th day, the four groups of RelyX Unicem or MaxCem cements presented similar mean values of fluoride release.

The fluoride release profile during the pH-cycling regimen for BisCem self-adhesive resin cement indicated that light activation reduced the fluoride release

Table 2: Mean (Standard Deviation) of Cumulative Amounts of Fluoride Ions Released ( $\mu\text{g}/\text{cm}^2$ ) From Resin Cements (Light or Self-cured) Over 15 Days <sup>a</sup>		
Resin Cements	Curing Mode	
	Light Activated	Autopolymerized
Panavia F. 2.0	9.5 (0.4) Aa	6.5 (0.1) Bb
RelyX Unicem	1.3 (0.2) Ab	1.3 (0.1) Ac
MaxCem	3.0 (0.2) Ab	2.7 (0.2) Ac
BisCem	8.9 (0.3) Ba	13.6 (0.6) Aa

<sup>a</sup> Similar letters (uppercase, row; lowercase, column) are not statistically different ( $p > 0.05$ ).

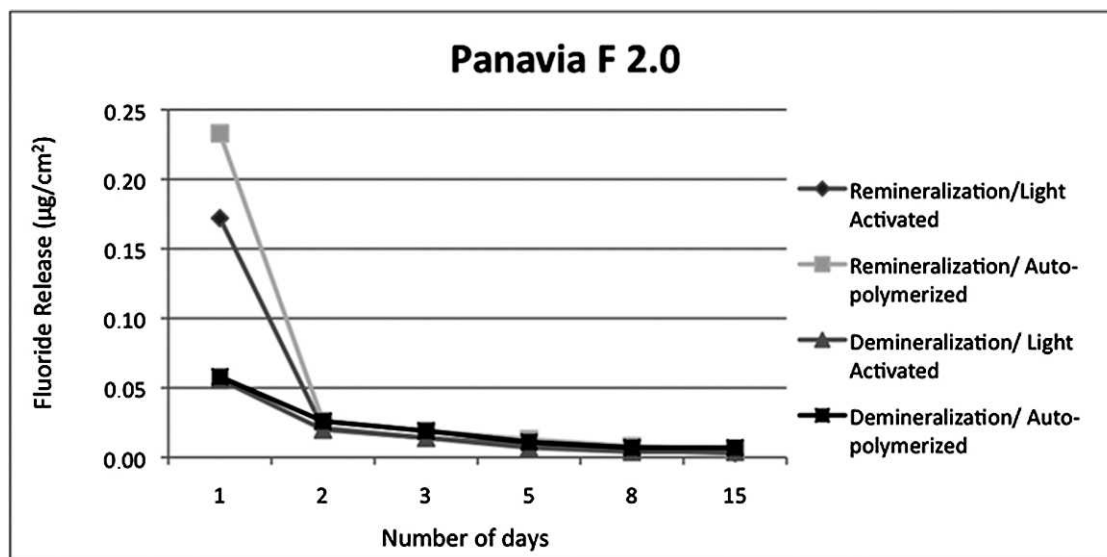


Figure 2. Fluoride-releasing behavior for Panavia F 2.0 during the pH-cycling regimen (fluoride released [ $\mu\text{g}/\text{cm}^2$ ] as a function of elapsed time for up to 15 days).

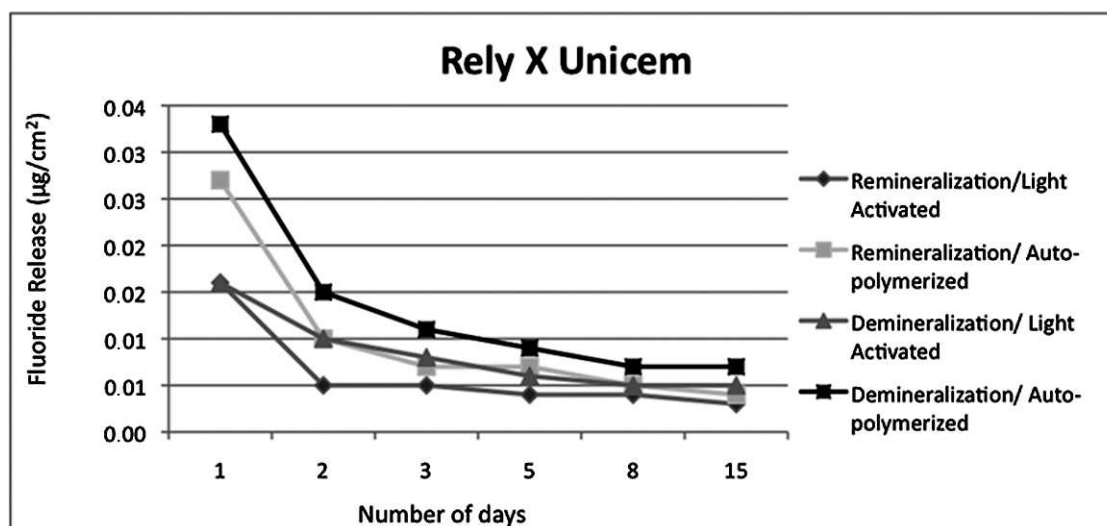


Figure 3. Fluoride-releasing behavior for RelyX Unicem during the pH-cycling regimen (fluoride released [ $\mu\text{g}/\text{cm}^2$ ] as a function of elapsed time for up to 15 days).

rate in both demineralizing and remineralizing solutions (Figure 5) at the first day. A low concentration of fluoride release was observed at the 15th day for all groups of BisCem cement (Figure 5).

## DISCUSSION

The first hypothesis was partially accepted since fluoride release from the resin cements, RelyX Unicem and MaxCem, was not influenced by the curing modes. These cements released the lowest amount of fluoride in water, and no differences were observed between them in either curing mode. The

water did not solubilize the high amount of fluoride ions from the polymerized resin matrix, even in an autopolymerizing mode that, theoretically, increases the resin matrix permeability for fluoride release.<sup>21</sup> On the other hand, BisCem had its fluoride release increased with the self-curing mode, and Panavia F 2.0 presented the opposite effect. BisCem and Panavia F 2.0 cements released more fluoride ions to water than RelyX Unicem and MaxCem self-adhesive resin cements in both curing modes. The composition of each resin cement, the solubility and permeability of the resin matrix, and the source,

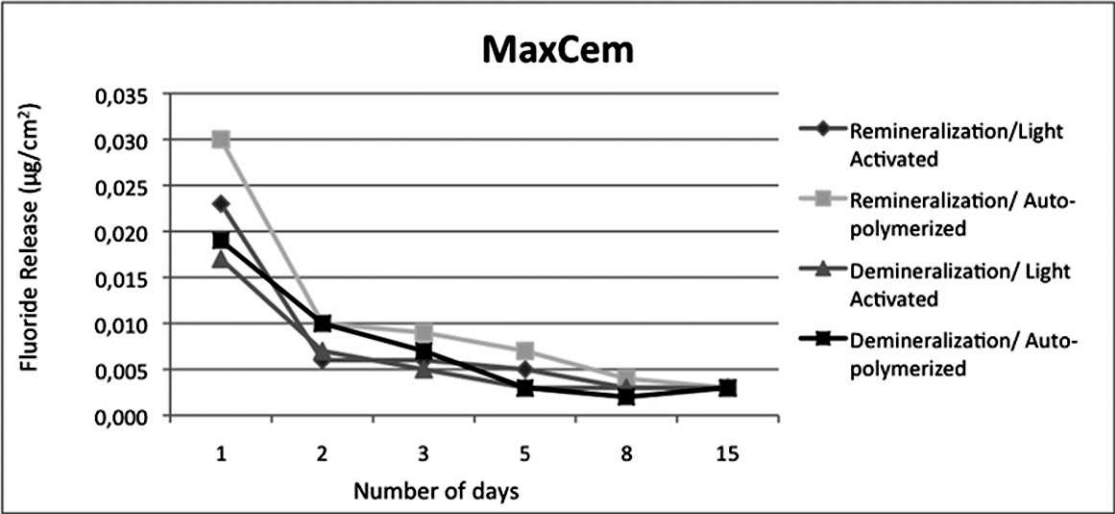


Figure 4. Fluoride-releasing behavior for MaxCem during the pH-cycling regimen (fluoride released [ $\mu\text{g}/\text{cm}^2$ ] as a function of elapsed time for up to 15 days).

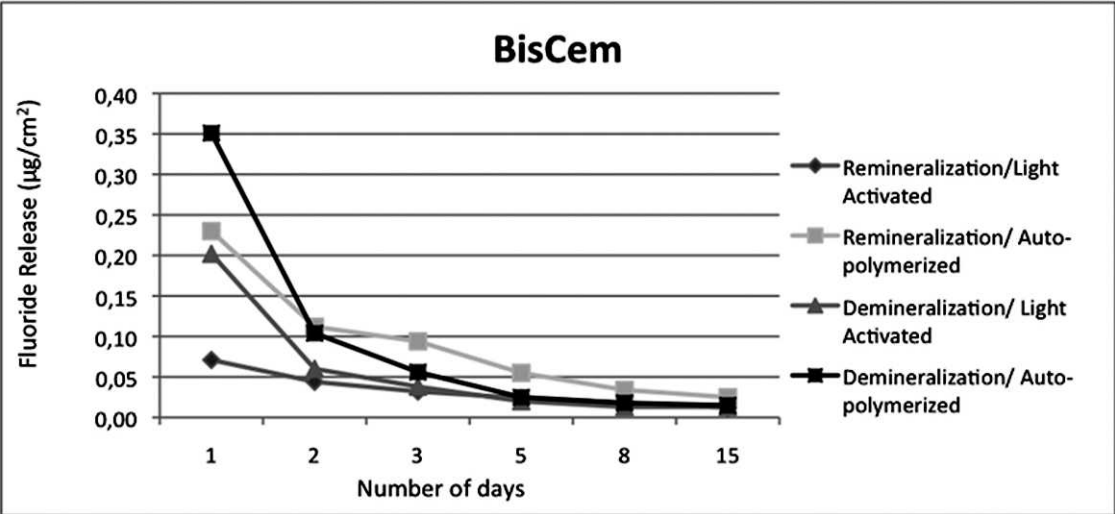


Figure 5. Fluoride-releasing behavior for BisCem during the pH-cycling regimen (fluoride released [ $\mu\text{g}/\text{cm}^2$ ] as a function of elapsed time for up to 15 days).

size, and concentration of the fluoride ions are important characteristics of the fluoride-releasing materials related to their ability to release the ions and, consequently, for the results of the first phase of this study.<sup>9,14,21-23</sup>

The fluoride source of Panavia F 2.0 is the sodium fluoride salt, which can be easily released by ionization when in contact with water or other aqueous solutions. For RelyX Unicem, the fluoride source is the glass powder, and the fluoride is available from similar acid-base reactions of glass ionomer cements.<sup>17,24,25</sup> MaxCem resin cement contains fluoroaluminosilicate particles that are similar

to the glass powder found in RelyX Unicem. The similar fluoride source of both materials may explain the similar cumulative rate of fluoride released in water for RelyX Unicem and MaxCem (Table 2). BisCem self-adhesive resin cement contains glass fillers, which can be composed of fluoride glass. The glass fillers are presented in both base and catalyst pastes of BisCem cement and may be in relative concentration, which explains the amount of fluoride released in water.

Several studies have reported that the glass powder serves as a reservoir of fluoride.<sup>26,27</sup> RelyX Unicem and MaxCem self-adhesive resin cements

that contain these glass particles undergo a significant reduction in fluoride release during pH cycling, but it did not tend to zero after 15 days of cycling. For Panavia F 2.0 and BisCem cements, very low concentrations of fluoride were detected at the last day of cycling, showing that releasing did not remain constant for 15 days and the fluoride source of these materials seems to be finite.<sup>21,22</sup> As observed in similar fluoridated resin-based studies,<sup>9,22,28</sup> higher ion release was observed on the initial days for all resin cements tested in this study, demonstrating that the fluoride release was not constant or uniform during the pH-cycling regimen (Figures 2-5). Since the fluoride release decreased throughout the duration of the study, regardless of the resin cement and the curing mode used, the second research hypothesis was rejected.

In this study, the storage medium (demineralizing or remineralizing solution) influenced the amount of fluoride released only for Panavia F 2.0 and MaxCem resin cements during pH cycling. At the first day, higher amounts of fluoride ions were observed in the remineralizing solution than in the demineralizing solution. These results significantly differ from the fluoride release behavior of glass ionomer cements during pH cycling, in which the fluoride release rate increases in acidic conditions (demineralizing solutions), especially in organic acids, such as acetic, lactic, and citric acid solutions.<sup>29-31</sup>

Yoda and others<sup>21</sup> demonstrated that the curing mode and storage medium influenced the amount and rate of fluoride release from fluoridated luting cements materials (Fuji II LC glass ionomer cement, GC Corp, Tokyo, Japan, and Panavia F resin cement, Kuraray Med). The authors stated that the light curing of the dual-cure resin cement was essential to enhance the mechanical properties and increase immediate bonding to tooth structures. However, when the polymerization is only chemical, an increase of fluoride release is observed since light activation enhances cross-linking density and network quality,<sup>32,33</sup> resulting in a reduction of resin matrix permeability for fluoride ion release.

The effects of curing modes on the degree of conversion of the same resin cements was previously evaluated by Aguiar, and the results for RelyX Unicem and BisCem self-adhesive resin cements showed that the autopolymerizing mode yielded a lower degree of conversion value than did light activation ( $p < 0.05$ ).<sup>34</sup> The lower degree of conversion of self-curing mode can increase the resin matrix permeability for fluoride release, which may explain the increase of fluoride from the self-cured

samples.<sup>21</sup> In both phases of this study (first phase, cumulative fluoride release rate in water; second phase, fluoride release profile during pH cycling), the BisCem cement released a higher fluoride concentration in self-curing mode. Conversely, the RelyX Unicem was not influenced by water media, and a higher concentration of fluoride was found for self-cured samples at the first day of pH cycling. Moreover, the acidic conditions of pH cycling possibly promoted more fluoride release. Since RelyX Unicem contains ionomeric components, this resin cement may show similar fluoride-releasing behavior as glass ionomer cements, which present an increased fluoride-releasing rate in acidic conditions.<sup>29-31</sup>

## CONCLUSION

The analysis of fluoride release from resin-based materials is complex and depends on some clinical variables that are not present in an evaluation of glass ionomer cements. Only one resin cement (BisCem) was affected by the curing mode in both storage conditions (water and pH cycling). This resin cement released a higher amount of fluoride in a self-curing mode. The storage conditions changed the fluoride release profile of Panavia F 2.0 and MaxCem resin cements. For all tested materials, the highest fluoride release was observed at initial days of the study, tending to gradually diminish with time, according to the profile of each material.

## Conflict of Interest Declaration

The Authors of this manuscript certify that they have no proprietary, financial or other personal interest of any nature or kind in any product, service and/or company that is presented in this article.

(Accepted 13 June 2011)

## REFERENCES

1. Stephen KW, McCall DR, & Tullis JI (1987) Caries prevalence in northern Scotland before, and 5 years after, water defluoridation *British Dental Journal* **163**(10) 324-326.
2. Attwood D, & Blinkhorn AS (1991) Dental health of schoolchildren 5 years after water fluoridation ceased in south-west Scotland *International Dental Journal* **41**(1) 43-48.
3. Mukai Y, & ten Cate JM (2002) Remineralization of advanced root dentin lesions *in vitro* *Caries Research* **36**(4) 275-280.
4. Levy SM (2003) An update on fluorides and fluorosis *Journal Canadian Dental Association* **69**(5) 286-291.
5. Tenuta LM, Zamataro CB, Del Bel Cury AA, Tabchoury CP, & Cury JA (2009) Mechanism of fluoride dentifrice

- effect on enamel demineralization *Caries Research* **43**(4) 278-285.
6. ten Cate JM, & van Duinen RN (1995) Hypermineralization of dentinal lesions adjacent to glass-ionomer cement restorations *Journal of Dental Research* **74**(6) 1266-1271.
  7. Hatibovic-Kofman S, Suljak JP, & Koch G (1997) Remineralization of natural carious lesions with a glass ionomer cement *Swedish Dental Journal* **21**(1-2) 11-17.
  8. Dionysopoulos P, Kotsanos N, Papadogiannis Y, & Konstantinidis A (1998) Artificial caries formation around fluoride-releasing restorations in roots *Journal of Oral Rehabilitation* **25**(11) 814-820.
  9. Hara AT, Queiroz CS, Freitas PM, Giannini M, Serra MC, & Cury JA (2005) Fluoride release and secondary caries inhibition by adhesive systems on root dentine *European Journal of Oral Sciences* **113**(3) 245-250.
  10. Anusavice KJ (2003) *Phillips' Science of Dental Materials* Elsevier, UK.
  11. Han L, Abu-Bakr N, Okamoto A, & Iwaku M (2001) Study of the fluoridated adhesive resin cement—Fluoride release, fluoride uptake and acid resistance of tooth structures *Dental Materials Journal* **20**(1) 114-122.
  12. Hicks J, Garcia-Godoy F, Donly K, & Flaitz C (2002) Fluoride-releasing restorative materials and secondary caries *Dental Clinics of North America* **46**(2) 247-276.
  13. Savarino L, Breschi L, Tedaldi M, Ciapetti G, Tarabusi C, Greco M, Giunti A, & Prati C (2004) Ability of restorative and fluoride releasing materials to prevent marginal dentine demineralization. *Biomaterials* **25**(6) 1011-1017.
  14. Burke FM, Ray NJ, & McConnell RJ (2006) Fluoride-containing restorative materials *International Dental Journal* **56**(1) 33-43.
  15. Pinto CF, Leme AF, Ambrosano GM, & Giannini M (2009) Effect of a fluoride- and bromide-containing adhesive system on enamel around composite restorations under high cariogenic challenge *in situ Journal of Adhesive Dentistry* **11**(4) 293-297.
  16. De Munck J, Vargas M, Van Landuyt K, Hikita K, Lambrechts P, & Van Meerbeek B (2004) Bonding of an auto-adhesive luting material to enamel and dentin *Dental Materials* **20**(10) 963-971.
  17. Goracci C, Cury AH, Cantoro A, Papacchini F, Tay FR, & Ferrari M (2006) Microtensile bond strength and interfacial properties of self-etching and self-adhesive resin cements used to lute composite onlays under different seating forces *Journal of Adhesive Dentistry* **8**(5) 327-335.
  18. Mazzitelli C, Monticelli F, Osorio R, Casucci A, Toledano M, & Ferrari M (2008) Effect of simulated pulpal pressure on self-adhesive cements bonding to dentin *Dental Materials* **24**(9) 1156-1163.
  19. Aguiar TR, Di Francescantonio M, Ambrosano GMD, & Giannini M (2010) Effect of curing mode on bond strength of self-adhesive resin luting cements to dentin *Journal of Biomedical Materials Research: Part B, Applied Biomaterials* **93**(1) 122-127.
  20. Carvalho AS, & Cury JA (1999) Fluoride release from some dental materials in different solutions *Operative Dentistry* **24**(1) 14-19.
  21. Yoda A, Nikaido T, Ikeda M, Sonoda H, Foxton RM, & Tagami J (2006) Effect of curing method and storage condition on fluoride ion release from a fluoride-releasing resin cement *Dental Materials Journal* **25**(2) 261-266.
  22. Attar N, & Turgut MD (2003) Fluoride release and uptake capacities of fluoride-releasing restorative materials *Operative Dentistry* **28**(4) 395-402.
  23. Wiegand A, Buchalla W, & Attin T (2007) Review on fluoride-releasing restorative materials—Fluoride release and uptake characteristics, antibacterial activity and influence on caries formation *Dental Materials* **23**(3) 343-362.
  24. Hikita K, Van Meerbeek B, De Munck J, Ikeda T, Van Landuyt K, Maida T, Lambrechts P, & Peumans M Bonding effectiveness of adhesive luting agents to enamel and dentin *Dental Materials* **23**(1) 71-80.
  25. Cantoro A, Goracci C, Papacchini F, Mazzitelli C, Fadda GM, & Ferrari M (2008) Effect of pre-cure temperature on the bonding potential of self-etch and self-adhesive resin cements *Dental Materials* **24**(5) 577-583.
  26. Itota T, Okamoto M, Sato K, Nakabo S, Nagamine M, Torii Y, & Inoue K (1999) Release and recharge of fluoride by restorative materials *Dental Materials Journal* **18**(4) 347-353.
  27. Peng D, Smales RJ, Yip HK, & Shu M (2000) *In vitro* fluoride release from aesthetic restorative materials following recharging with APF gel *Australian Dental Journal* **45**(3) 198-203.
  28. de Araujo FB, García-Godoy F, Cury JA, & Conceição EN (1996) Fluoride release from fluoride-containing materials *Operative Dentistry* **21**(5) 185-190.
  29. Matsuya S, Matsuya Y, Yamamoto Y, & Yamane M (1984) Erosion process of a glass ionomer cement in organic acids *Dental Materials Journal* **3**(2) 210-219.
  30. De Moor RJ, & Verbeeck RM (1998) Effect of acetic acid on the fluoride release profiles of restorative glass ionomer cements *Dental Materials* **14**(4) 261-268.
  31. De Moor RJ, Martens LC, & Verbeeck RM (2005) Effect of a neutral citrate solution on the fluoride release of conventional restorative glass ionomer cements *Dental Materials* **21**(4) 318-323.
  32. Shimura R, Nikaido T, Yamauchi M, Ikeda M, & Tagami J (2005) Influence of curing method and storage condition on microhardness of dual-cure resin cements *Dental Materials Journal* **24**(1) 70-75.
  33. Arrais CA, Rueggeberg FA, Waller JL, de Goes MF, & Giannini M (2008) Effect of curing mode on the polymerization characteristics of dual-cured resin cement systems *Journal of Dentistry* **36**(6) 418-426.
  34. Aguiar TR, Di Francescantonio M, Arrais CA, Ambrosano GM, Davanzo C, & Giannini M (2010) Influence of curing mode and time on degree of conversion of one conventional and two self-adhesive resin cements *Operative Dentistry* **35**(3) 295-299.